

Phonon-induced decay of the electron spin in quantum dots

Vitaly N. Golovach, Alexander Khaetskii, and Daniel Loss

*Department of Physics and Astronomy, University of Basel,
Klingelbergstrasse 82, CH-4056 Basel, Switzerland*

(Dated: February 2, 2008)

We study spin relaxation and decoherence in a GaAs quantum dot due to spin-orbit interaction. We derive an effective Hamiltonian which couples the electron spin to phonons or any other fluctuation of the dot potential. We show that the spin decoherence time T_2 is as large as the spin relaxation time T_1 , under realistic conditions. For the Dresselhaus and Rashba spin-orbit couplings, we find that, in leading order, the effective magnetic field can have only fluctuations transverse to the applied magnetic field. As a result, $T_2 = 2T_1$ for arbitrarily large Zeeman splittings, in contrast to the naively expected case $T_2 \ll T_1$. We show that the spin decay is drastically suppressed for certain magnetic field directions and values of the Rashba coupling constant. Finally, for the spin coupling to acoustic phonons, we show that $T_2 = 2T_1$ for all spin-orbit mechanisms in leading order in the electron-phonon interaction.

PACS numbers: 72.25.Rb, 73.21.La, 03.67.Lx

Phase coherence of spin in quantum dots (QDs) is of central importance for spin-based quantum computation in the solid state [1, 2]. Sufficiently long coherence times are needed for implementing quantum algorithms and error correction schemes. If the qubit is operated as a classical bit, its decay time is given by the spin relaxation time T_1 , which is the time of a spin-flip process. For quantum computation, however, the spin decoherence time T_2 — the lifetime of a coherent superposition of spin up and spin down states — must be sufficiently long. In semiconductor QDs, the spin coherence is limited by the dot *intrinsic* degrees of freedom, such as phonons, spins of nuclei, excitations on the Fermi surface (e.g. in metallic gates), fluctuating impurity states nearby the dot, electromagnetic fields, etc. It is well known (and experimentally verified) that the T_1 time of spin in QDs is extremely long, extending up to $100 \mu\text{s}$. The decoherence time T_2 , in its turn, is limited by both spin-flip and dephasing processes, and can be much smaller than T_1 , although its upper bound is $T_2 \leq 2T_1$. Knowledge of the mechanisms of spin relaxation and decoherence in QDs can allow one to find regimes with the least spin decay.

Recently, the spin relaxation time T_1 in a single-electron GaAs QD was measured [3] by means of a pulsed relaxation measurement technique (PRMT) [4]. This technique was previously applied to measure the triplet-to-singlet spin relaxation in a two-electron quantum dot [5], yielding a spin relaxation time of $200 \mu\text{s}$. The application of the PRMT to Zeeman sublevels became possible with resolving the Zeeman splitting in *dc* transport spectroscopy [3, 6], which required a magnetic field $B > 5 \text{ T}$. The results of Ref. 3 show that $T_1 > 50 \mu\text{s}$ at $B = 7.5 \text{ T}$ and 14 T , with no indication of a B -field dependence. Experimental values for the spin T_2 time in a single QD are not available yet, but an ESR scheme for its measurement has been proposed [7]. The ensemble spin decoherence time T_2^* was measured in *n*-doped GaAs bulk semiconductors [8], demonstrating coherent spin preces-

sion over times exceeding $T_2^* \sim 100 \text{ ns}$. This indicates that the decoherence time of a single spin is even larger, $T_2 \geq T_2^*$. However, the mechanisms of spin decoherence for extended and localized electrons are rather different (cf. Ref. 9) and, therefore, the result of Ref. 8 is not conclusive for electrons in QDs.

Different mechanisms of spin relaxation in QDs have been considered, such as spin-phonon coupling via spin-orbit [10, 11] or hyperfine interaction [12], and spin-nuclear coupling [13, 14, 15]. The spin-orbit mechanisms yield no spin decay at $B = 0$, due to the Kramers degeneracy of the dot states. Interestingly, for GaAs QDs, the orbital effect of B leads to no spin decay in lowest order in spin-orbit interaction [10, 11, 16, 17]. This is due to the special form (linear in momentum) of the spin-orbit coupling in two-dimensions (2D). The leading order contribution is, thus, proportional to the Zeeman splitting and leads to long spin-flip times T_1 in GaAs QDs varying strongly with the B -field [10]. However, previous theories do not apply to the high values of B used in recent experiments [3], and thus, no comparison could be made so far. As for the nuclear mechanism, the electron spin decay can be suppressed by applying a B -field or by polarizing the nuclear system [13, 14].

In this Letter, we show that the spin T_2 time, caused by spin-orbit interaction in GaAs QDs, is as large as the spin T_1 time. We assume low temperatures, $T \ll \hbar\omega_0$, where $\hbar\omega_0$ is the size-quantization energy of the dot, and with no external noise in the applied magnetic field B . We, thus, argue that the lower bound $T_1 \geq 50 \mu\text{s}$ established in Ref. 3 is, in fact, also a lower bound for T_2 . Furthermore, we show that the spin decay can be reduced by a special choice of direction of $\mathbf{B}$, if there is Rashba spin-orbit interaction.

The Hamiltonian describing the electron in a QD reads

$$H = H_d + H_Z + H_{SO} + U_{ph}, \quad (1)$$

$$H_d = \frac{p^2}{2m^*} + U(\mathbf{r}), \quad (2)$$

$$H_{SO} = \beta(-p_x\sigma_x + p_y\sigma_y) + \alpha(p_x\sigma_y - p_y\sigma_x), \quad (3)$$

$$H_Z = \frac{1}{2}g\mu_B\mathbf{B} \cdot \boldsymbol{\sigma}, \quad (4)$$

where $\mathbf{p} = -i\hbar\nabla + (e/c)\mathbf{A}(\mathbf{r})$ is the electron 2D kinetic momentum, $U(\mathbf{r})$ is the lateral confining potential, with $\mathbf{r} = (x, y)$, and $\boldsymbol{\sigma}$ are the Pauli matrices. The axes x and y point along the main crystallographic directions in the (001) plane of GaAs. The spin-orbit coupling is given by the Hamiltonian (3), where the term proportional to β originates from the bulk Dresselhaus spin-orbit coupling, which is due to the absence of inversion symmetry in the GaAs lattice; the term proportional to α represents the Rashba spin-orbit coupling, which can be present in quantum wells if the confining potential (in our case along the z -axis) is asymmetric. The magnetic field $\mathbf{B} = B(\sin\theta\cos\varphi, \sin\theta\sin\varphi, \cos\theta)$ defines the spin quantization axis via the Zeeman term (4). The phonon potential is given by

$$U_{ph}(\mathbf{r}) = \sum_{\mathbf{q}j} \frac{F(q_z)e^{i\mathbf{q}_{\parallel}\mathbf{r}}}{\sqrt{2\rho_c\omega_{qj}/\hbar}}(e\beta_{\mathbf{q}j} - iq\Xi_{\mathbf{q}j})(b_{-\mathbf{q}j}^\dagger + b_{\mathbf{q}j}) \quad (5)$$

where $b_{\mathbf{q}j}^\dagger$ creates an acoustic phonon with wave vector $\mathbf{q} = (\mathbf{q}_{\parallel}, q_z)$, branch index j , and dispersion ω_{qj} ; ρ_c is the sample density [volume is set to unity in (5)]. The factor $F(q_z)$ equals unity for $|q_z| \ll d^{-1}$ and vanishes for $|q_z| \gg d^{-1}$, where d is the characteristic size of the quantum well along the z -axis. We take into account both piezo-electric ($\beta_{\mathbf{q}j}$) and deformation potential ($\Xi_{\mathbf{q}j}$) kinds of electron-phonon interaction. For $\beta_{\mathbf{q}j}$ and $\Xi_{\mathbf{q}j}$, we refer the reader to Ref. 18. Next, we derive an effective Hamiltonian, which describes the spin dynamics, decoherence and relaxation at low temperatures $T \ll \hbar\omega_0$.

The electron spin couples to phonons due to the spin-orbit interaction (3). For typical GaAs QDs the spin-orbit length $\lambda_{SO} = \hbar/m^*\beta$ is much larger than the electron orbit size λ . In 2D, there is no linear in λ/λ_{SO} contribution to the spin-phonon coupling at zero Zeeman splitting [10, 11, 16, 17]. Here, we consider a finite magnetic field, $m^*\beta^2 \ll g\mu_B B \ll \hbar\omega_0$, for which the linear in λ/λ_{SO} contribution to the spin-phonon coupling dominates the spin decay. Using perturbation theory (or Schrieffer-Wolff transformation), we obtain the effective Hamiltonian [19]

$$H_{\text{eff}} = \frac{1}{2}g\mu_B(\mathbf{B} + \delta\mathbf{B}(t)) \cdot \boldsymbol{\sigma}, \quad (6)$$

$$\delta\mathbf{B}(t) = 2\mathbf{B} \times \boldsymbol{\Omega}(t), \quad (7)$$

where $\boldsymbol{\Omega}(t)$ is defined as follows

$$\boldsymbol{\Omega}(t) = \langle\psi| \left[\left(\hat{L}_d^{-1} \boldsymbol{\xi} \right), U_{ph}(t) \right] |\psi\rangle. \quad (8)$$

Here, $|\psi\rangle$ is the electron orbital wave function, $\hat{L}_d$ is the dot Liouvillean, $\hat{L}_d A = [H_d, A]$. The vector $\boldsymbol{\xi}$ has

a simple form in the coordinate frame: $x' = (x+y)/\sqrt{2}$, $y' = -(x-y)/\sqrt{2}$, $z' = z$, namely, $\boldsymbol{\xi} = (y'/\lambda_-, x'/\lambda_+, 0)$, where $1/\lambda_{\pm} = m^*(\beta \pm \alpha)/\hbar$. Eq. (7) contains one of our main results: *in 1st order in spin-orbit interaction, there can be only transverse fluctuations of the effective magnetic field, i.e. $\delta\mathbf{B}(t) \cdot \mathbf{B} = 0$* . This statement holds true for spin coupling to any fluctuations, be it the noise of a gate voltage or coupling to particle-hole excitations in a Fermi sea. Next, we consider the decay of the electron spin, $\mathbf{S} = \boldsymbol{\sigma}/2$, governed by the Hamiltonian (6).

The phonons which are emitted or absorbed by the electron leave the dot during a time τ_c , $d/s \lesssim \tau_c \lesssim \lambda/s$, where s is the sound velocity. The electron spin decays over a much longer time span in typical structures, and, therefore, undergoes many uncorrelated scattering events. In this regime, the dynamics and decay of the spin is governed by the Bloch equation [20]

$$\langle\dot{\mathbf{S}}\rangle = \boldsymbol{\omega} \times \langle\mathbf{S}\rangle - \Gamma\langle\mathbf{S}\rangle + \boldsymbol{\Upsilon}, \quad (9)$$

where $\boldsymbol{\omega} = \omega\mathbf{l}$, with $\omega = g\mu_B B/\hbar$ and $\mathbf{l} = \mathbf{B}/B$. For a generic $\delta\mathbf{B}(t)$, we find that in the Born-Markov approximation [20, 21] the tensor Γ_{ij} can be written as $\Gamma = \Gamma^r + \Gamma^d$, with

$$\begin{aligned} \Gamma_{ij}^r &= \delta_{ij}(\delta_{pq} - l_p l_q) J_{pq}^+(\omega) - (\delta_{ip} - l_i l_p) J_{pj}^+(\omega) \\ &\quad - \delta_{ij} \varepsilon_{kpq} l_k I_{pq}^-(\omega) + \varepsilon_{ipq} l_p I_{qj}^-(\omega), \end{aligned} \quad (10)$$

$$\Gamma_{ij}^d = \delta_{ij} l_p l_q J_{pq}^+(0) - l_i l_p J_{pj}^+(0), \quad (11)$$

where $J_{ij}^{\pm}(w) = \text{Re}[J_{ij}(w) \pm J_{ij}(-w)]$ and $I_{ij}^{\pm}(w) = \text{Im}[J_{ij}(w) \pm J_{ij}(-w)]$ are given by the spectral function

$$J_{ij}(w) = \frac{g^2 \mu_B^2}{2\hbar^2} \int_0^{+\infty} \langle \delta B_i(0) \delta B_j(t) \rangle e^{-iwt} dt. \quad (12)$$

The inhomogeneous part in Eq. (9) is given by

$$\begin{aligned} 2\boldsymbol{\Upsilon}_i &= l_j J_{ij}^-(\omega) - l_i J_{jj}^-(\omega) + \varepsilon_{ipq} I_{pq}^+(\omega) \\ &\quad + \varepsilon_{iqk} l_k l_p [I_{pq}^+(\omega) - I_{pq}^+(0)], \end{aligned} \quad (13)$$

where ε_{ijk} is the anti-symmetric tensor (with Einstein summation convention) and we have assumed that $\langle\delta\mathbf{B}(t)\rangle = 0$. Eq. (9) describes spin decay in a number of problems, such as electron scattering off impurities in bulk systems, nuclear spin scattering [20], etc. In our notation, the spin decay comes from the symmetric part of Γ , whereas the anti-symmetric part leads to a correction to $\boldsymbol{\omega}$ in Eq. (9). The tensor Γ^r describes spin decay due to processes of energy relaxation, such as, e.g., emission/absorption of a phonon. Therefore, the T_1 time is entirely determined by Γ^r , see below. The tensor Γ^d can be non-zero only due to elastic scattering of spin, i.e. due to dephasing. Γ^d contributes to the decoherence time T_2 , and so does Γ^r . In many cases, however, the latter contribution is negligible, and Γ^d entirely dominates the spin decoherence [20]. This is in strong contrast to what we

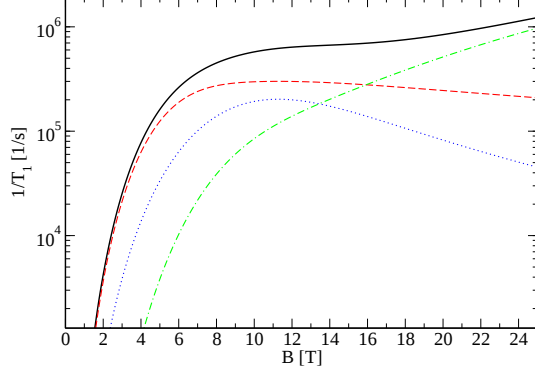


FIG. 1: Solid curve: the relaxation rate $1/T_1$, given in Eq. (21), as a function of the B -field for a GaAs QD with $\hbar\omega_0 = 1.1$ meV, $\lambda_{SO} = \hbar/m^*\beta = 1 \mu\text{m}$, and $\alpha = 0$. The direction of $\mathbf{B}$ is in plane, $\mathbf{B} = (B_x, B_y, 0)$. The dashed (dotted) curve shows the contribution of the transverse (longitudinal) phonons interacting with the electron via the piezo-electric ($\bar{\beta}_{j\vartheta}$) mechanism. The dot-dashed curve shows the contribution of the longitudinal phonons interacting via the deformation potential ($\bar{\Xi}_j$) mechanism. The angular dependence of $1/T_1$ is given by Eq. (22), the square of an ellipsoid.

find here for an electron localized in a QD. To illustrate this, we first consider an example when Γ^d dominates the spin decoherence and then return to our case. A textbook example is $\langle \delta B_i(0) \delta B_j(t) \rangle = \bar{b}^2 \delta_{ij} \exp(-|t|/\tau_c)$. Choosing $\mathbf{l} = (0, 0, 1)$, we obtain from Eqs. (10) - (12) the non-zero elements: $\Gamma_{xx}^r = \Gamma_{yy}^r = \Gamma_{zz}^r/2 = \gamma_n^2 \bar{b}^2 \tau_c / (1 + \omega^2 \tau_c^2)$, and $\Gamma_{xx}^d = \Gamma_{yy}^d = \gamma_n^2 \bar{b}^2 \tau_c$, where $\gamma_n = g\mu_B/\hbar$. The longitudinal component $\langle S_z \rangle$ decays over the time $T_1 = \Gamma_{zz}^{-1} = 1/\Gamma_{zz}^r$. The transverse components decay over the time $T_2 = 1/(\Gamma_{xx}^r + \Gamma_{xx}^d)$. At $\omega \gg 1/\tau_c$, the contribution of Γ_{xx}^r to T_2 is negligible, and hence, $T_2 \ll T_1$. The latter relation has widely been quoted in the literature on quantum computation. In stark contrast to this example, we show now below that there are no *intrinsic* dephasing mechanisms for our case, which would justify this relation for the electron spin in GaAs QDs at $T \ll \hbar\omega_0$.

We start with calculating the spin decay due to the mechanism (7). Here, Γ_{ij}^d is identically zero, due to the transverse nature of the fluctuating field $\delta\mathbf{B}$. This can be inferred from Eqs. (11) and (12), noticing that each term in (11) contains $\mathbf{l} \cdot \delta\mathbf{B} = 0$. In order to calculate Γ_{ij}^r , we first find the main axes of the tensor $J_{ij}(w)$, see Eq. (12). $J_{ij}(w)$ is diagonal in the frame (X, Y, Z) , which is obtained from (x', y', z) by a rotation with Euler angles φ' , θ , and χ . Here, the angles $\varphi' = \varphi - \pi/4$ and θ give $\mathbf{B}$ in the frame (x', y', z) , and χ depends on the details of the dot confining potential $U(\mathbf{r})$. It can be determined from $\langle \delta B_X \delta B_Y(t) \rangle = 0$. Assuming $U(\mathbf{r}) = U(r)$, we find [22]

$$\tan 2\chi = \frac{2(\lambda_+^2 - \lambda_-^2) l_{x'} l_{y'} l_z}{\lambda_+^2 (l_{y'}^2 - l_z^2 l_{x'}^2) + \lambda_-^2 (l_{x'}^2 - l_z^2 l_{y'}^2)}. \quad (14)$$

We now consider a harmonic confinement, $U(r) = m^* \omega_0^2 r^2 / 2$, and evaluate $\Omega(t)$ of Eq. (8) for the ground state $\psi(\mathbf{r}) = \exp(-r^2/2\lambda^2) / \lambda\sqrt{\pi}$, where $\lambda^{-2} = \hbar^{-1} \sqrt{(m^* \omega_0)^2 + (eB_z/2c)^2}$. Using the identity [23]

$$y = \frac{2}{m^* \omega_0^2} \hat{L}_d \left(\frac{\partial}{\partial y} + \frac{ieB_z}{\hbar c} x \right), \quad (15)$$

we find an expression for $\Omega_{x'}$, which can be obtained from the r.h.s. of Eq. (5) by replacing

$$\exp(i\mathbf{q}_{\parallel}\mathbf{r}) \rightarrow \frac{2iq_{y'}}{m^* \omega_0^2 \lambda_-} \exp(-q_{\parallel}^2 \lambda^2 / 4). \quad (16)$$

Furthermore, an expression for $\Omega_{y'}$ is obtained in the same way, using the substitution (16) with a different prefactor, namely with $(q_{y'}/\lambda_-) \rightarrow (q_{x'}/\lambda_+)$. Finally, for the real part of the correlator $J_{ij}(w)$, we obtain

$$\text{Re} J_{XX}(w) = \frac{\omega^2 w^3 (N_w + 1)}{(\Lambda_+ m^* \omega_0^2)^2} \sum_j \frac{\pi \hbar^3}{\rho_0 s_j^5} \int_0^{\pi/2} d\vartheta \sin^3 \vartheta \times e^{-(w \lambda \sin \vartheta)^2 / 2s_j^2} \left| F \left(\frac{|w|}{s_j} \cos \vartheta \right) \right|^2 \left(e^2 \bar{\beta}_{j\vartheta}^2 + \frac{w^2}{s_j^2} \bar{\Xi}_j^2 \right), \quad (17)$$

where $N_w = (e^{\hbar w/T} - 1)^{-1}$, and s_j is the sound velocity for branch j . For GaAs, we use $s_1 \approx 4.7 \times 10^5$ cm/s and $s_2 = s_3 \approx 3.37 \times 10^5$ cm/s. Furthermore, $\bar{\Xi}_j = \delta_{j,1} \Xi_0$ with $\Xi_0 \approx 7$ eV, and $\bar{\beta}_{1,\vartheta} = 3\sqrt{2}\pi h_{14} \kappa^{-1} \sin^2 \vartheta \cos \vartheta$, $\bar{\beta}_{2,\vartheta} = \sqrt{2}\pi h_{14} \kappa^{-1} \sin 2\vartheta$, $\bar{\beta}_{3,\vartheta} = \sqrt{2}\pi h_{14} \kappa^{-1} (3 \cos^2 \vartheta - 1) \sin \vartheta$, with $h_{14} \approx 0.16$ C/m² and $\kappa \approx 13$. The effective spin-orbit length Λ_+ in Eq. (17) is given by

$$\frac{2}{\Lambda_{\pm}^2} = \frac{1 - l_{x'}^2}{\lambda_-^2} + \frac{1 - l_{y'}^2}{\lambda_+^2} \pm \sqrt{\left(\frac{1 - l_{x'}^2}{\lambda_-^2} + \frac{1 - l_{y'}^2}{\lambda_+^2} \right)^2 - \frac{4l_z^2}{\lambda_+^2 \lambda_-^2}}. \quad (18)$$

$\text{Re} J_{YY}(w)$ is obtained from Eq. (17) by substituting $\Lambda_+ \rightarrow \Lambda_-$, and $J_{ZZ}(w) = 0$. $\text{Im} J_{XX}(w)$ and $\text{Im} J_{YY}(w)$ are irrelevant for our discussion, see further. From Eq. (10), we obtain $\Gamma_{XX}^r = J_{YY}^+(\omega)$, $\Gamma_{YY}^r = J_{XX}^+(\omega)$, $\Gamma_{ZZ}^r = J_{XX}^+(\omega) + J_{YY}^+(\omega)$, $\Gamma_{XY}^r = -I_{YY}^-(\omega)$, $\Gamma_{YX}^r = I_{XX}^-(\omega)$. Since $\Gamma_{ij}/\omega \sim \omega \lambda^2 / \omega_0 \Lambda_{\pm}^2 \ll 1$, we can solve the secular equation iteratively and obtain [24]

$$\frac{1}{T_1} := l_p l_q \Gamma_{pq} = \Gamma_{ZZ}, \quad (19)$$

$$\frac{1}{T_2} := \frac{1}{2} (\delta_{pq} - l_p l_q) \Gamma_{pq} = \frac{1}{2} (\Gamma_{XX} + \Gamma_{YY}). \quad (20)$$

Then, the solution of Eq. (9) reads $\langle S_X(t) \rangle = S_{\perp} e^{-t/T_2} \sin(\omega t + \phi)$, $\langle S_Y(t) \rangle = S_{\perp} e^{-t/T_2} \cos(\omega t + \phi)$, and $\langle S_Z(t) \rangle = S_T + (S_Z^0 - S_T) e^{-t/T_1}$, with the thermodynamic value of spin being $\mathbf{S}_T = \mathbf{l}(\mathbf{l} \cdot \mathbf{Y}) T_1 = -(\mathbf{l}/2) \tanh(\hbar\omega/2k_B T)$, and the initial value $\langle \mathbf{S}(0) \rangle = (S_{\perp} \sin \phi, S_{\perp} \cos \phi, S_Z^0)$. For our special situation with purely transverse fluctuations ($\Gamma^d = 0$), we obtain

$$\frac{1}{T_1} = \frac{2}{T_2} = J_{XX}^+(\omega) + J_{YY}^+(\omega). \quad (21)$$

Keeping in mind the setup of Ref. 3, we plot the relaxation rate $1/T_1$ as a function of B for $\theta = \pi/2$ and $\alpha = 0$ on Fig. 1 (solid curve). We find that $1/T_1$ has a plateau in a wide range of magnetic fields (cf. Ref. 3), due to a crossover from the piezoelectric-transverse (dashed curve) to the deformation potential (dot-dashed curve) mechanism of electron-phonon interaction. For arbitrary φ , θ , and α , we have $1/T_1 = f/T_1(\theta = 0, \alpha = 0)$ with

$$f = \frac{1}{\beta^2} [(\alpha^2 + \beta^2)(1 + \cos^2 \theta) + 2\alpha\beta \sin^2 \theta \sin 2\varphi] \quad (22)$$

The angular dependence of $1/T_1$ for $\alpha = 0$ has been obtained before [10]. Note that $\sqrt{f}$ describes an ellipsoid in the frame (x', y', z) , i.e. $f = x'^2 + y'^2 + z^2$, with dimensionless x', y', z obeying $(x'/a)^2 + (y'/b)^2 + (z/c)^2 = 1$, where $a = 1 + \alpha/\beta$, $b = 1 - \alpha/\beta$, and $c = \sqrt{a^2 + b^2}$. Note that, if $\alpha = \beta$, then $b = 0$, i.e. $1/T_1$ vanishes if the B -field is along y' . The same is true along the x' axis for $\alpha = -\beta$. This special case ($\alpha = \pm\beta$) has been discussed previously for extended electron states in a two-dimensional electron gas (2DEG) [25]. Note that the Hamiltonian (1) conserves the spin component $\sigma_{y'(x')}$ for $\alpha = \beta$ ($\alpha = -\beta$) and $\mathbf{B} \parallel y'(x')$. This spin conservation results in T_1 being infinite to all orders in the spin-orbit Hamiltonian (3). At the same time, the decoherence rate $1/T_2$ reduces to the next order contribution of (3). However, as we show below, a single-phonon process is inefficient in inducing dephasing and, therefore, $1/T_2$ can be non-zero only in the next order in electron-phonon interaction. Next, we note that a long lived spin state also occurs in a different GaAs structure, namely, for a 2DEG grown in the (110) crystallographic direction. Then, the normal to the 2DEG plane component of spin is conserved [26], provided there is no Rashba coupling.

We discuss now other spin-orbit mechanisms. In Eq. (3), we did not include the so-called k^3 -terms of the Dresselhaus spin-orbit coupling [26], i.e. $H_{SO} \propto \beta d^2 (\sigma_x \{k_x, k_y^2\} - \sigma_y \{k_y, k_x^2\})$. They are parametrically small ($d^2/\lambda^2 \ll 1$) in the 2D limit, compared to the retained ones. However, their contribution to the spin decay can be important, if $g \lesssim d^2/\lambda^2$ and $\lambda^2 \ll d\lambda_{SO}$, since the orbital effect of the magnetic field contributes here in the first place. Still, for typical GaAs QDs, these mechanisms are negligible.

Additional spin decay mechanisms arise from the *direct* spin-phonon interaction [10]. The strain field produced by phonons couples to the electron spin via the spin-orbit interaction, resulting in the term $\Delta H' = (V_0/4)\varepsilon_{ijk}\sigma_i\{u_{ij}, p_k\}$, where p_i is the bulk kinetic momentum, u_{ij} is the phonon strain tensor, and $V_0 = 8 \times 10^7$ cm/s for GaAs. A similar mechanism occurs in a B -field, due to g -factor fluctuations caused by lattice distortion. This yields $\Delta H'' = \tilde{g}\mu_B \sum_{i \neq j} u_{ij}\sigma_i B_j$, where $\tilde{g} \approx 10$ for GaAs. The contribution of these mechanisms to the spin-flip rates in QDs has been estimated in Ref. 10. Except for the $\alpha = \pm\beta$ cases discussed

above, the direct mechanisms are usually negligible in QDs. Here, we find that such spin-phonon couplings do not violate the equality $T_2 = 2T_1$ [27]. For this, we note that $\Gamma_{ij}^d = 0$ for a generic $\delta B_i = \sum_{\mathbf{q}} M_i(\mathbf{q})(b_{-\mathbf{q}}^\dagger + b_{\mathbf{q}})$ in Eq. (6), if $q|M(\mathbf{q})|^2 \rightarrow 0$ at $q \rightarrow 0$. Obviously, this condition is satisfied for the direct spin-phonon mechanisms, since the strain tensor u_{ij} vanishes at $q = 0$. The same follows for the Hamiltonian (1) with the phonon potential (5) and an arbitrary H_{SO} ; the physical explanation being that the potential of long-wave phonons is constant over the dot size and, thus, commutes with H_{SO} . Finally, we note that, at temperatures $T \sim \hbar\omega_0$, there can be dephasing mechanisms [28], which can result in $T_2 \ll T_1$.

In conclusion, we have shown that the decoherence time T_2 of an electron spin in a GaAs QD is as large as the relaxation time T_1 for the spin decay based on spin-orbit mechanisms. We acknowledge support from the Swiss NSF, NCCR Basel, EU RTN 'Spintronics', US DARPA, ARO, and ONR.

-
- [1] D. Loss and D.P. DiVincenzo, Phys. Rev. A **57**, 120 (1998); cond-mat/9701055.
 - [2] D.D. Awschalom, D. Loss, and N. Samarth, eds., *Semiconductor Spintronics and Quantum Computing* (Springer, New York, 2002).
 - [3] R. Hanson *et al.*, cond-mat/0303139.
 - [4] T. Fujisawa *et al.*, Phys. Rev. Lett. **88**, 236802 (2002).
 - [5] T. Fujisawa *et al.*, Nature **419**, 278 (2002).
 - [6] R.M. Potok *et al.*, Phys. Rev. Lett. **91**, 016802 (2003).
 - [7] H. Engel and D. Loss, Phys. Rev. Lett. **86**, 4648 (2001).
 - [8] J. M. Kikkawa and D. D. Awschalom, Phys. Rev. Lett. **80**, 4313 (1998).
 - [9] G.E. Pikus and A.N. Titkov, in *Optical Orientation*, North-Holland, Amsterdam, p.73 (1984).
 - [10] A.V. Khaetskii and Yu.V. Nazarov, Phys. Rev. B **64**, 125316 (2001).
 - [11] A.V. Khaetskii and Yu.V. Nazarov, Phys. Rev. B **61**, 12639 (2000).
 - [12] S.I. Erlingsson and Yu.V. Nazarov, Phys. Rev. B **66**, 155327 (2002).
 - [13] G. Burkard, D. Loss, and D. P. DiVincenzo, Phys. Rev. B **59**, 2070 (1999).
 - [14] A.V. Khaetskii, D. Loss, and L. Glazman, Phys. Rev. Lett. **88**, 186802 (2002); Phys. Rev. B **67** 195329 (2003).
 - [15] I.A. Merkulov, A.L. Efros, and M. Rosen, Phys. Rev. B **65**, 205309 (2002).
 - [16] B.I. Halperin *et al.*, Phys. Rev. Lett. **86**, 2106 (2001).
 - [17] I.L. Aleiner and V.I. Fal'ko, Phys. Rev. Lett. **87**, 256801 (2001).
 - [18] V.F. Gantmakher and Y.B. Levinson, *Carrier Scattering in Metals and Semiconductors* (North-Holland, Amsterdam, 1987).
 - [19] In leading order in H_{SO} , we have $\tilde{H} \equiv e^S H e^{-S} = H_d + H_Z + U_{ph} + [S, U_{ph}]$, with S given by $[H_d + H_Z, S] = H_{SO}$. Then, $H_{\text{eff}} = \langle \psi | \tilde{H} | \psi \rangle$ up to a spin independent part.
 - [20] C.P. Slichter, *Principles of Magnetic Resonance*, (Springer-Verlag, Berlin, 1980).

- [21] For non-Markovian effects in the spin-boson model, see D. Loss and D.P. DiVincenzo, cond-mat/0304118.
- [22] We fix the quadrant of χ by requiring that the sign of $\sin 2\chi$ coincides with the one of the numerator of Eq. (14).
- [23] A similar identity for x is obtained from Eq. (15) by replacing (x, y) by $(-y, x)$.
- [24] The decay rates are defined by the secular equation: $\det ||\Gamma_{ij} - E\delta_{ij} + \varepsilon_{ijk}\omega_k|| = 0$, as the real part of E . In the secular approximation, one iterates the secular equation, assuming $\Gamma_{ij}/\omega \ll 1$.
- [25] J. Schliemann, J.C. Egues, and D. Loss, Phys. Rev. Lett. **90**, 146801 (2003).
- [26] M.I. D'yakonov and V.Yu.Kachorovskii, Sov. Phys. Semicond. **20**, 110 (1986).
- [27] This was first argued in A.V. Khaetskii, D. Loss, and L. Glazman, J. Supercond. **16**, 221 (2003).
- [28] Y.G. Semenov and K.W. Kim, cond-mat/0310125.